

# THERMAL TRANSPORT IN FERROMAGNETIC $\text{La}_{1-X}\text{AE}_X\text{MnO}_3$ WITH LARGE DIVALENT IONS\*

H. FUJISHIRO, M. IKEBE, S. KANOH AND H. OZAWA

Faculty of Engineering, Iwate University  
 4-3-5 Ueda, Morioka 020-8551, Japan

*(Received July 10, 2002)*

The thermal conductivity  $\kappa(T)$  of the  $\text{La}_{1-X}\text{AE}_X\text{MnO}_3$  manganites (AE: divalent ions;  $\text{Ca}^{2+}$ ,  $\text{Sr}^{2+}$ ,  $\text{Pb}^{2+}$ ,  $\text{Ba}^{2+}$ ) has been measured. For small AE ions ( $\text{Ca}^{2+}$  and  $\text{Sr}^{2+}$ ),  $\kappa(T)$ , which is dominated by the phonon contribution, shows an enhancement below the ferromagnetic metal transition temperature  $T_c$ . In contrast, the enhancement is completely wiped out for the largest  $\text{Ba}^{2+}$  ion. The increase of the ionic radius of AE ions reduces the average static lattice distortion with the tolerance factor  $\Gamma$  approaching to 1, while it increases the randomness of ionic radii in the  $(\text{La}_{1-X}\text{AE}_X)$ -site cations defined by the cation radius variance  $\sigma^2$ . In the  $\text{Ba}^{2+}$  system, the  $\kappa(T)$  reduction caused by the largest  $\sigma^2$  masks out the  $\kappa(T)$  enhancement characteristic of the ferromagnetic-metal manganite systems.

PACS numbers: 65.40.-b; 75.30.Kz; 72.15.Eb

## 1. Introduction

As recently revived studies on perovskite-based manganese have confirmed,  $(\text{RE}_{1-X}\text{AE}_X)\text{MnO}_3$ -type crystals (RE= trivalent rare-earth ions such as  $\text{La}^{3+}$ ,  $\text{Pr}^{3+}$ ; AE= divalent ions such as  $\text{Ca}^{2+}$ ,  $\text{Sr}^{2+}$ ) undergo a variety of dramatic phenomena such as the colossal magnetoresistance (CMR) and the insulator-metal (I-M) transition [1], etc. The phonon thermal conductivity  $\kappa_{\text{ph}}(T)$  is a valuable tool to investigate the effect of the lattice dynamics on the phase transitions of the manganite system [2, 3]. In the  $\text{La}_{1-X}\text{Ca}_X\text{MnO}_3$  (LCMO) system, for example, the thermal conductivity  $\kappa(T)$  increases abruptly below the ferromagnetic metal (FM-M) transition temperature  $T_c$  for  $0.19 \leq X \leq 0.30$  [4]. The increase of the AE-ion radius ( $r_{\text{AE}}$ ) in the  $\text{ABO}_3$  perovskite manganites results in the reduction of the static lattice distortion from the cubic structure with the tolerance factor

---

\* Presented at the International Conference on Strongly Correlated Electron Systems, (SCES 02), Cracow, Poland, July 10–13, 2002.

$\Gamma$  ( $= (r_A + r_O) / (\sqrt{2}(r_B + r_O))$ ) approaching 1, where  $r_A$ ,  $r_B$  and  $r_O$  are the atomic radii of  $A$ -site ( $\text{La}_{1-X}\text{AE}_X$ ) ion,  $B$ -site ( $\text{Mn}^{3+}_{1-X}\text{Mn}^{4+}_X$ ) ion and oxygen, respectively. The  $\Gamma$  value affects the  $T_c$  value through the one electron bandwidth  $W$  and the widened  $W$  enhances  $T_c$  as the lattice approaches to cubic. On the other hand,  $T_c$  also depends on the size differences within the  $A$ -site ( $\text{La}^{3+}$  and  $\text{AE}^{2+}$ ) cations, even if  $\Gamma$  is kept constant [5]. The randomness of the  $A$ -site cations is defined by the  $A$ -site cation radius variance  $\sigma^2$  ( $= \sum y_i r_i^2 - r_A^2$ ,  $y_i$  is the fractional occupancy of the  $A$ -site species and  $r_A$  is the average ionic radius of  $A$ -site cations) and  $\sigma^2$  increases with increasing  $AE$ -site ionic radius in the present La-based manganites. In this paper,  $\kappa(T)$  of  $\text{La}_{1-X}\text{AE}_X\text{MnO}_3$  is studied for various sizes of the  $AE$  ions. We discuss the origin of the  $\kappa(T)$  anomalies below  $T_c$  from the point of view of the lattice distortions.

## 2. Experimental

$\text{La}_{1-X}\text{AE}_X\text{MnO}_3$  samples ( $\text{AE} = \text{Ba}^{2+}, \text{Pb}^{2+}, \text{Sr}^{2+}, \text{Ca}^{2+}$ ) were prepared by a solid-state reaction method for the hole concentration  $X = 0.1 \sim 0.5$ . The sizes of  $r_{\text{AE}}$  are  $r(\text{Ca}^{2+}) < r(\text{Sr}^{2+}) < r(\text{Pb}^{2+}) < r(\text{Ba}^{2+})$  and  $\Gamma$  and  $\sigma^2$  were calculated using the tabulated radii with ninefold coordination [6]. The samples were fabricated by solid state reaction method at  $1500^\circ\text{C}$  for 8 h in air [4, 8]. The grain size of each sample is about  $10 \sim 20 \mu\text{m}$  and is independent of the species of  $AE$  ions and the hole concentration  $X$ . The thermal conductivity  $\kappa(T)$  was measured by a steady-state heat flow method using a Gifford–McMahon (GM) cycle helium refrigerator as a cryostat.

## 3. Results and discussion

Figure 1 shows  $\kappa(T)$  of  $\text{La}_{1-X}\text{AE}_X\text{MnO}_3$  samples ((a)  $X = 0.20$  and (b)  $X = 0.30$ ). All the samples show the metallic electrical conduction below the FM-M transition temperature  $T_c$  [4, 7, 8]. For  $X = 0.20$ ,  $\kappa(T)$  of the  $\text{Ca}^{2+}$ ,  $\text{Sr}^{2+}$  and  $\text{Pb}^{2+}$  systems, which is overwhelmingly due to the phonon contribution, shows a characteristic enhancement below  $T_c$  ( $= 200 \text{ K}$  for  $\text{AE} = \text{Ca}^{2+}$  and  $= 330 \text{ K}$  for  $\text{AE} = \text{Sr}^{2+}$ ) and then reaches a maximum at around  $T \approx 40 \text{ K}$ . These anomalous temperature dependences are considered to result from the reduction in the phonon scattering related to the relaxation of the spatially random Jahn–Teller (J-T) distortion in the metallic phase. With initial increase of  $r_{\text{AE}}$  from  $\text{AE} = \text{Ca}^{2+}$  to  $\text{AE} = \text{Sr}^{2+}$ , the absolute values of  $\kappa(T)$  remarkably increases, which suggests that the increase of  $r_{\text{AE}}$  enhances the phonon thermal conduction possibly by reducing the lattice distortion from cubic. It is to be noticed that the crystal structure is orthorhombic for LCMO and changes to rhombohedral for the

$La_{1-X}Sr_XMnO_3$  (LSMO) system. With further increase of  $r_{AE}$ , however, the absolute value of  $\kappa(T)$  is reduced significantly. For the  $Ba^{2+}$  system (LBMO) with the largest  $r_{AE}$ ,  $\kappa(T)$  monotonically decreases with the decrease in temperature. For  $X = 0.30$  shown in Fig. 1(b), the  $\kappa(T)$  maximum at low temperatures is enhanced for LCMO and LSMO, but it is strongly suppressed for the  $Pb^{2+}$  system (LPMO). A comparison of high temperature  $\kappa(T)$  around 300 K for  $X = 0.20$  and  $X = 0.30$  shows that  $\kappa(T)$  values of LPMO and LBMO are somewhat enhanced with increasing  $X$ . This enhancement is far clearer for LBMO, which may suggest that the  $\kappa$  enhancing effect related to increasing  $\Gamma$  is still at work in these two systems at the high temperatures [8].

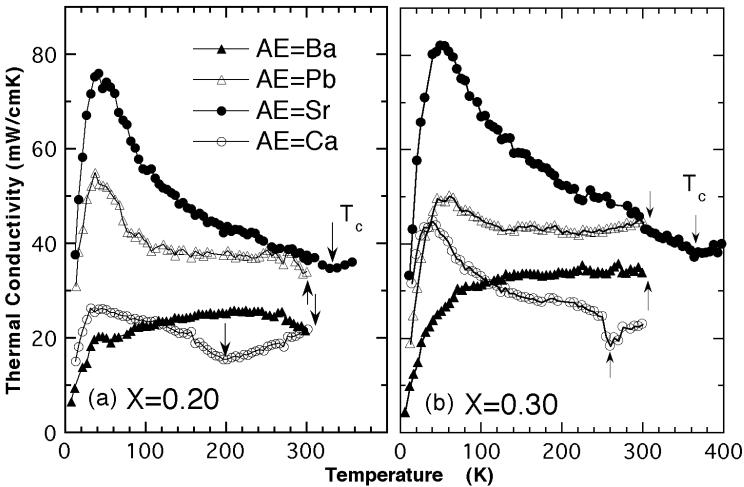


Fig. 1. Thermal conductivity  $\kappa(T)$  of  $La_{1-X}AE_XMnO_3$  ((a):  $X = 0.20$ , (b):  $X = 0.30$ ) for various sizes of AE ions. Arrows show  $T_c$  which was magnetically determined.

Figure 2 presents the calculated values of (a)  $\Gamma$  and (b)  $\sigma^2$ , as a function of the hole concentration  $X$ .  $\Gamma$  increases with increasing  $X$  and with increasing  $r_{AE}$ , which may tend to bring about the  $\kappa(T)$  enhancement. On the other hand,  $\sigma^2$ , the randomness of the  $A$ -site cations, also increases with increasing  $X$  and  $r_{AE}$ . The increase in  $\sigma^2$  corresponds to the increase of the randomness of the local lattice distortion and should reduce  $\kappa(T)$ . In Fig. 1,  $\kappa(T)$  of LBMO is smaller than those of other systems at low temperatures. This result suggests that the reduction mechanism due to the large  $\sigma^2$  value is very strong in the  $Ba^{2+}$  system especially at low temperatures. least at low temperatures.

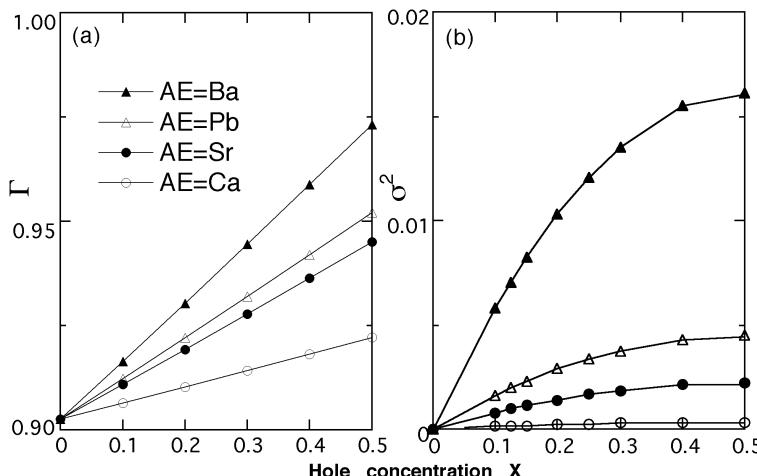


Fig. 2. Calculated values of (a) tolerance factor  $\Gamma$  and (b) cation radius variance  $\sigma^2$  as a function of hole concentration  $X$ .

In summary, the increase of the AE ion radius brings about both enhancing and reducing effects on the phonon thermal conductivity. In the  $\text{Ba}^{2+}$  system with the largest AE ion radius, the effect of the  $\kappa(T)$  reduction due to the large  $\sigma^2$  values may be more dominant than the  $\kappa(T)$  enhancing effect due to the large  $\Gamma$  value. In the  $\text{Pb}^{2+}$  system, the reduction effect seems to be dominant at low temperatures.

## REFERENCES

- [1] Y. Tomioka, A. Asamitsu, Y. Moritomo, H. Kuwahara, Y. Tokura, *Phys. Rev. Lett.* **74**, 5108 (1995).
- [2] J.L. Cohn, J.J. Neumeier, C.P. Popoviciu, K.J. MacClellan, Th. Leventouri, *Phys. Rev. B* **56**, R8495 (1997).
- [3] J. Hejtmanek, Z. Jirak, Z. Arnold, M. Marysko, S. Krupicka, C. Martin, F. Damay, *J. Appl. Phys.* **83**, 7204 (1998).
- [4] H. Fujishiro, M. Ikebe, *Physics in Local Lattice Distortion*, American Institute of Physics, New York 2001, p.433.
- [5] L.M. Rodrigues-Martinez, J.P. Attfield, *Phys. Rev. B* **54**, R15622 (1996).
- [6] R.D. Shannon, *Acta Cryst. A* **32**, 751 (1976).
- [7] M. Ikebe, H. Fujishiro, Y. Konno, *J. Phys. Soc. Jpn.* **67**, 1083 (1998).
- [8] H. Fujishiro, S. Kanoh, M. Ikebe, *J. Phys. Soc. Jpn.* **71**, Suppl. 142 (2002).